


Four arm mesylate terminated Poly ethylene oxide

| | | |
|---------------------------------|------|--------------------------|
| Mn x 10 ³ (total) | PDI | _SO2CH3 Functionality |
| 9.5 | 1.08 | >99% |

The polymer was prepared by anionic living polymerization of ethylene oxide using pentaerythritol potassium salt as the initiator. The scheme of the reaction is illustrated below:

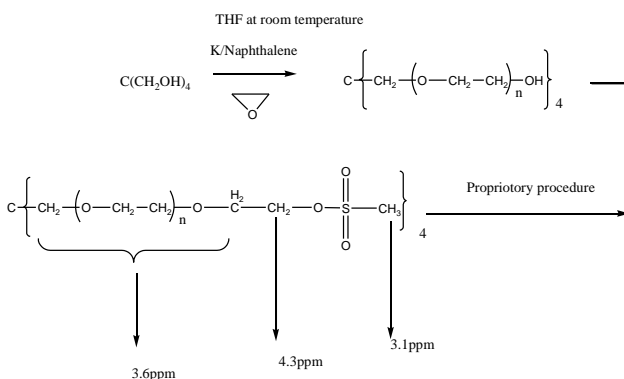

By Size exclusion chromatography (SEC): Varian liquid chromatograph equipped with UV and refractive detector. SEC columns from Supelco were used with THF containing 2 vol% (Et)₃N as the eluent. The molecular weights were determined using light scattering detector and viscosity detector. The molecular weights and the polydispersity index were calculated.

Purification of the obtained polymer:

1. Dissolved the polymer in de-ionized distilled water to remove the any insoluble organic catalyst side product.
2. Polymer extracted from water with dichloromethane.

3. Polymer solution in dichloromethane was dried over anhydrous sodium sulfate.
4. Solution filtered and then passed through a column packed with basic Al_2O_3 .
5. Solution concentrated on rota-evaporator
6. Solution precipitated in cold diethyl ether.
7. Dried under vacuum for 48h at 38 oC.

Polymer is soluble in THF, water and CHCl_3 . The polymer is insoluble in hexane, ether, cold isopropanol and cold ethanol.

HNMR of the Mesitylate four arm PEG

