


Sample Name: Poly(isoprene-b-ethylene oxide)

Sample #: P18834A-IPEO

(poly isoprene block rich in 1,2 & 3,4 microstructure)

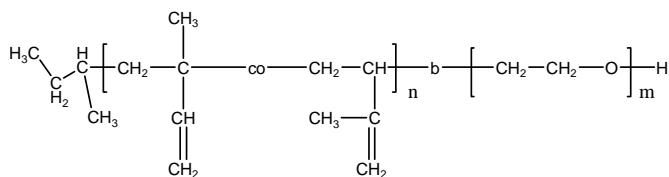

Composition:

$Mn \times 10^3$	Mw/Mn (PDI)
21.5-b-7.0	1.10

Synthesis Procedure:

Poly(isoprene-b-ethylene oxide) was prepared by anionic polymerization process.


Characterization:

OH terminated isoprene was analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from ^1H NMR spectroscopy by comparing the peak area of the vinylic butadiene protons at about 5.4 ppm with the ethylene oxide protons at 3.6 ppm. Block copolymer PDI is determined by SEC.

Solubility:

Poly(isoprene-b-ethylene oxide) is soluble in THF, CHCl_3 , and toluene. The polymer has variable solubility in hexane, methanol, ethanol and water depending on its composition.


^1H NMR spectrum of the sample

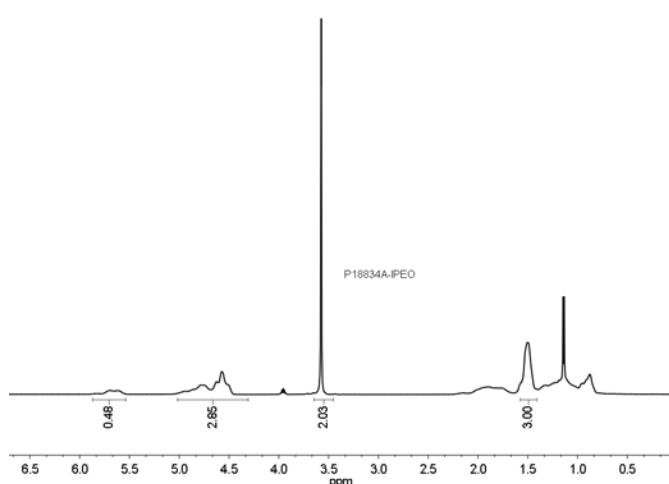


SEC elogram of polyisoprene block:

Sample ID: P18834-IPOH

Concentration (mg/mL)	0.7397
Sample dr/dc (mL/g)	0.1250
Method File	PS80K-august 5-2014-0000.vcm
Column Set	3xPL 1113-6300
Solvent	THF

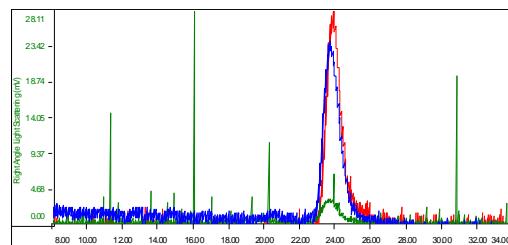


Sample	Mn	Mw	Mp	Mw/Mn	IV
P18836_01.vdt	21,393	27,269	19,862	1.275	0.2058

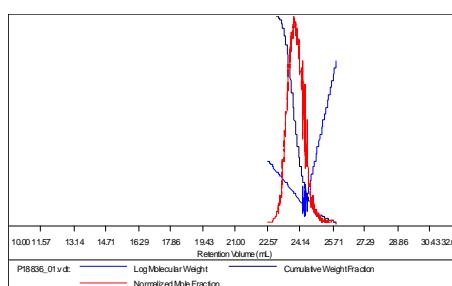

SEC elogram of PI-PEO diblock copolymer:

Sample ID: P18834A-IPEC

Concentration (mg/mL)	6.7816
Sample dr/dc (mL/g)	0.0950
Method File	PS80K-august 12-2014-0000.vcm
Column Set	3xPL 1113-6300
Solvent	THF

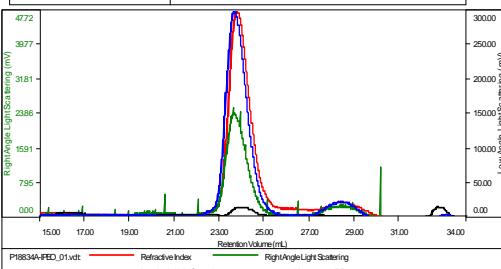

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18834A-IPEO_01.vdt	28,996	31,971	31,767	1.103	0.2020

