


**Sample Name:**  
**ω-Hydroxy Terminated Polystyrene**

**Sample #: P18901 SOH**

**Structure:**

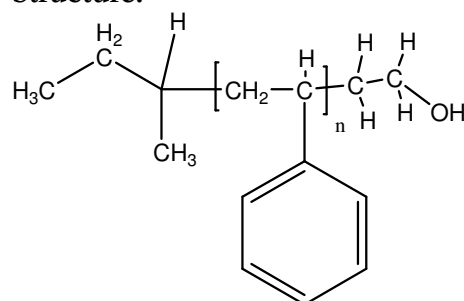

**Composition:**

Mn x 10 <sup>3</sup>	PDI
10.5	1.06
T <sub>g</sub> (°C)	80

**Synthesis Procedure:**

ω-hydroxy terminated polystyrene was prepared by living anionic polymerization using OH protected initiator.

**Characterization:**

The molecular weight and polydispersity index of this polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector. Polymer functionality was determined by titration with NaOH solution using phenolphthalein as the indicator.

**Thermal analysis:**


Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T<sub>g</sub>) has been considered.

**Solubility:**

Polymer is soluble in toluene, THF, CHCl<sub>3</sub> and can be precipitated in water and cold methanol.

**SEC of Sample:**  
**Sample ID: P18901-SOH**

Concentration (mg/mL)	20.8399
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-0923-2014-0000.vcm
Column Set	3x PL 1113-6000
Solvent	THF

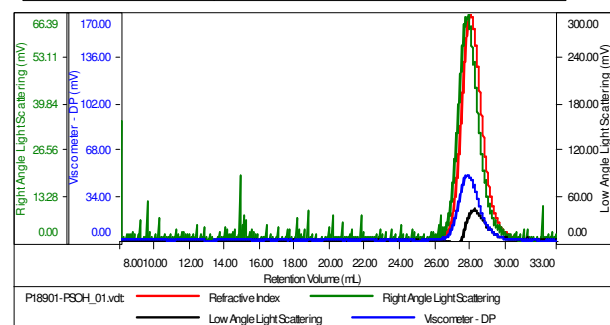

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P18901-PSOH_01.vcl	10,691	11,317	10,901	1.059	0.0724

**DSC thermogram for the sample:**

