


Sample Name: Poly(styrene-*b*- N-methyl 4-vinyl pyridine iodide)

Sample #: P3192-S4VPQ

Structure:

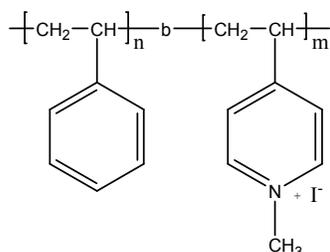


Composition:

Mn x 10 ³ PS- <i>b</i> -P4VPQ	PDI
535- <i>b</i> -175	1.2

Synthesis Procedure:

Poly(styrene-*b*-4-vinyl pyridine) is prepared by living anionic polymerization in THF or THF-DMF solvent mixtures at -78 °C. Polystyrene macroanions were end capped with a unit of diphenyl ethylene (DPE) before adding 4-vinylpyridine (4VP) monomer. For further details please see our published articles.^{1,2} The scheme of the reaction is illustrated below:

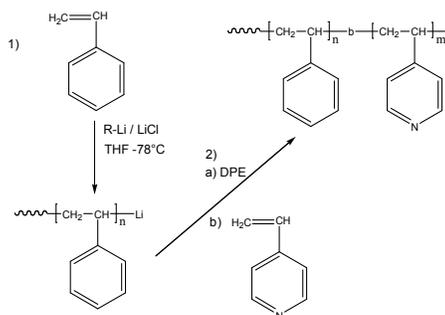

Characterization:


Polymer was analyzed by size exclusion chromatography (SEC) in DMF to obtain the molecular weight and polydispersity index (PDI). The composition of the block copolymer was determined by titration in acetic acid/HClO₄ using crystal violet indicator. Copolymer PDI is determined by SEC.

Quaternization.

Polymer was dissolved in distilled DMF. Distilled methyl iodide was added 2 molar excess. The quaternized polymer was precipitated into hexane, filtered and washed with hexane several times. It was dried under vacuum for 8 h., the yield of the

polymer indicating quantitative quaternization. Fourier transform infrared spectroscopy was performed on a Nicolet Impact 400D. The quaternization is confirmed by the disappearance of the pyridine band at 1412cm⁻¹.

SEC of Sample precursor P3191-S4VP:

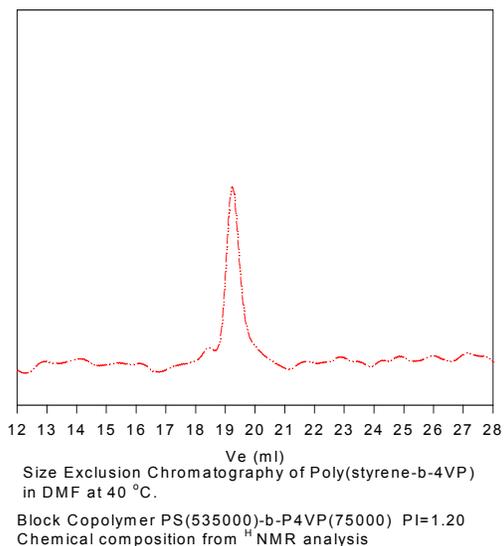

References:

- (1). S. K. Varshney, X. F. Zhong and A. Eisenberg *Macromolecules*, **1993**, 26, 701-706.
- (2). Z.Gao, S. K. Varshney, S. Wong, A. Eisenberg *Macromolecules*, **1994**, 27, 7923-7927.