


Sample Name:

Poly(n-butyl methacrylate-b-2-hydroxy ethyl methacrylate)

Sample #: P10553-nBuMAHEMA

Structure:

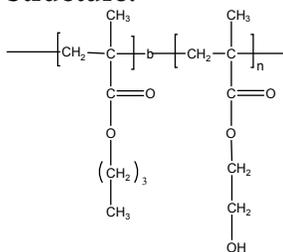

Composition:

$M_n \times 10^3$ nBuMA-b-HEMA	PDI
39-b--b-10.0	1.25
T_g for nBuMA block: 53 °C	T_g for HEMA block: 103 °C

Synthesis Procedure:

Poly(n-butyl methacrylate-b-2-hydroxy ethyl methacrylate) block copolymer is synthesized by living anionic polymerization with sequential addition of n-butyl methacrylate and protecting hydroxyl HEMA (trimethyl siloxy ethyl methacrylate monomer). The obtained polymer was precipitated in methanol/acidic to deprotect the hydroxyl group.

Characterization:

SEC analysis of the obtained block copolymer in THF in presence of triethyl amine as eluent resulting in an ambiguity of the result because some of the trimethylsiloxy ethyl methacrylate units are deprotected to convert hydroxy ethyl methacrylate.

The final block copolymer composition by $^1\text{H-NMR}$ spectroscopy in CdCl_2 also yield the uncertainty of the analysis because of poor solubility of poly HEMA block in CdCl_2 . The composition of the obtained polymer therefore, carried out in CdCl_2 after protecting the OH group with acetic anhydride by comparing the peak area CH_2 alkyl ester (4 protons) group at 1.6 and 1.5 ppm and subtracting 6 protons values for nBuMA monomers (3 from $\alpha\text{-CH}_3$ and 3 protons from terminal CH_3 alkyl ester group) between 0.9ppm to 1.2ppm to calculate 3 protons ($\alpha\text{-CH}_3$) from HEMA monomers. Block copolymer PDI is determined by SEC.



Thermal analysis:

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of $10^\circ\text{C}/\text{min}$. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T_g).

Solubility:


Polymer is soluble in DMF, THF.

$^1\text{H-NMR}$ Spectrum of the block in DMF:

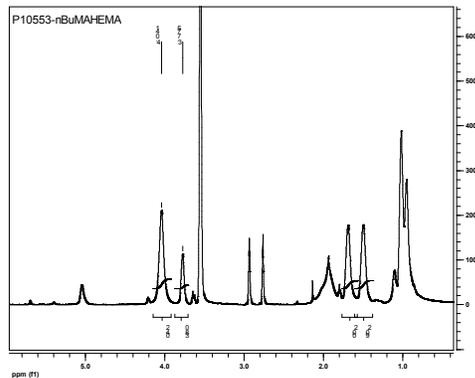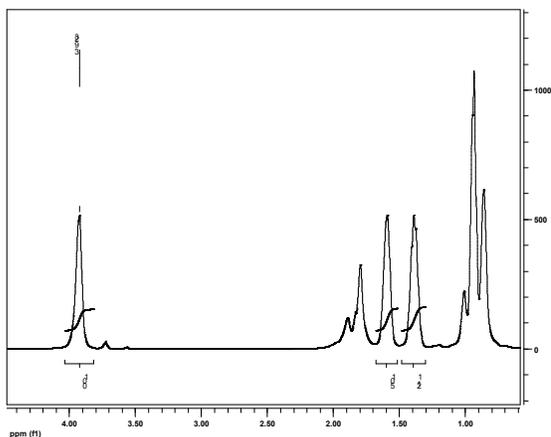


SEC of the First Block:


Concentration (mg/mL)	5.0517
Sample dn/dc (mL/g)	0.0810
Method File	PS80K-Oct-0000.vcm
Column Set	3x PL 1113-8300
System	System 1

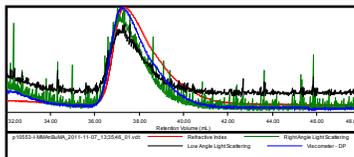

Sample	M_n (Da)	M_w (Da)	M_p (Da)	M_w/M_n	IV (dL/g)
p10553-I-MMA/nBuMA_2011-11-07_13:3	38,108	48,377	55,550	1.269	0.3297

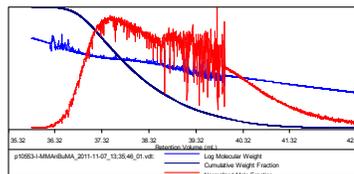

P10553--nBuMAHEMA

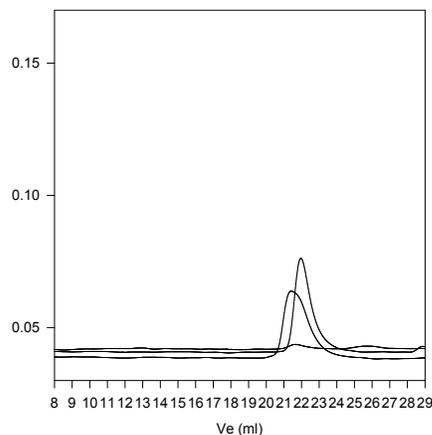

Size exclusion chromatography of
1. Poly nBuMA: M_n 39,000 M_w : 48,000 M_w/M_n 1.25
Poly(nBuMA)-b- Poly 2-Hydroxy ethyl methacrylate (Protected with TMS)
 M_n 39,000-b-15,000 M_w/M_n 1.2
After Deprotection of HEMA TMS : M_n 39,000-b-10,000 M_w/M_n 1.25
The deprotected polymer does not elute in THF.

DSC thermogram for the polymer:

