


Sample Name: Poly(methyl methacrylate -b- N,N-dimethyl acrylamide)

Sample #: P7243-MMADMA

Structure:

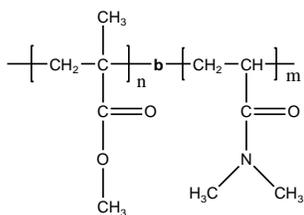


Composition:

Mn x 103 PMMA-b-PDMA	PDI
36.9-b-4	1.19
Tg for MMA: 120oC	Tg for DMA: Not distinct

Synthesis Procedure:

Poly(methyl methacrylate -b- dimethyl acrylamide) is prepared by living anionic polymerization with sequence addition of methyl methacrylate followed by N,N-dimethyl acrylamide. The scheme of the reaction is illustrated below:

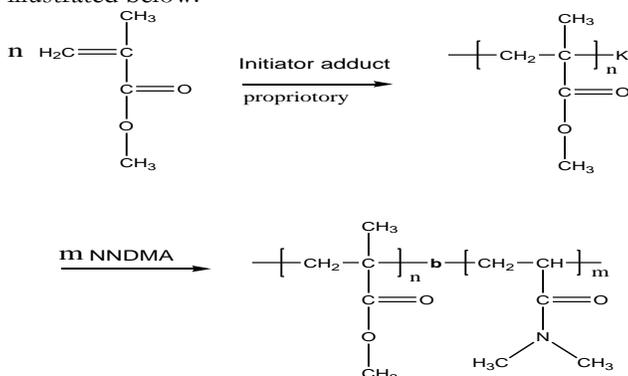

Characterization:

An aliquot of the anionic poly(methyl methacrylate) block was terminated before addition of N,N-dimethyl acrylamide and analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from 1H-NMR spectroscopy by comparing the peak area of the methyl methacrylate protons at 3.6 ppm with the peak area of the dimethyl acrylamide (N-(CH3)2) protons at 2.8-3.2 ppm. Copolymer PDI is determined by SEC in DMF as eluent at 40°C.

Purification of the Polymer:

The obtained polymer was precipitated in cold methanol or in Hexane/Ethanol cold depending on the compositions. The polymer was re-dissolved in CHCl3 and wash with water. The polymer was dried in toluene/THF using rota-evaporator. The solution was precipitated in Hexane. The polymer dried at 40 oC under vacuum.


Thermal analysis:

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (Tg).

Solubility:


Poly(methyl methacrylate- b- N,N-dimethyl acrylamide) is soluble in CHCl3, THF and in DMF

1H-NMR Spectrum of the block copolymer:

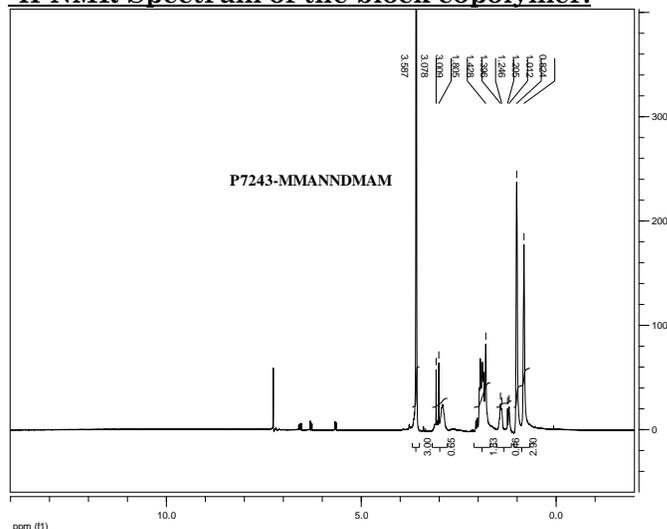

SEC of the block copolymer:

P7243-MMADMA

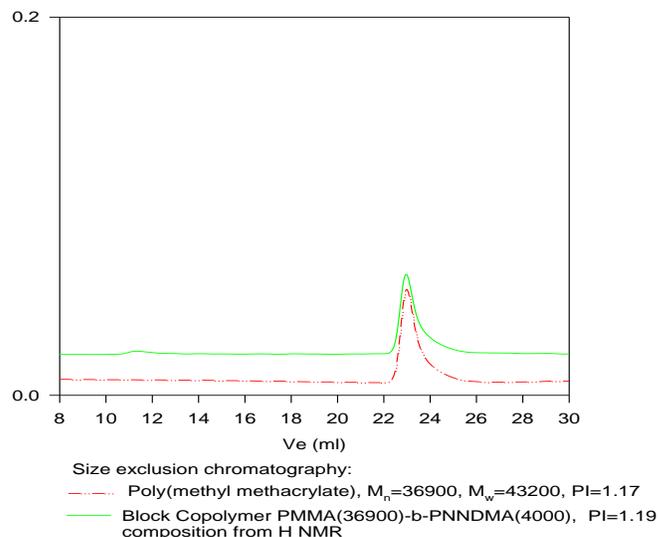

DSC thermogram for MMA block:

