


**Sample Name:** Poly(ethylene oxide-b-dimethyl siloxane -b- ethylene oxide)

**Sample #:** P7306-EODMSEO

**Structure:**




**Composition:**

Mn x 10 <sup>3</sup> PEO-b-PDMS-b-PEO (k)	PDI
5.0-2.0-5.0	1.2

**Synthesis Procedure:**

The polymer is prepared by hydrosilylation reaction of ally PEO and disilane terminated PDMS using Pt catalyst. The reaction scheme is shown below:

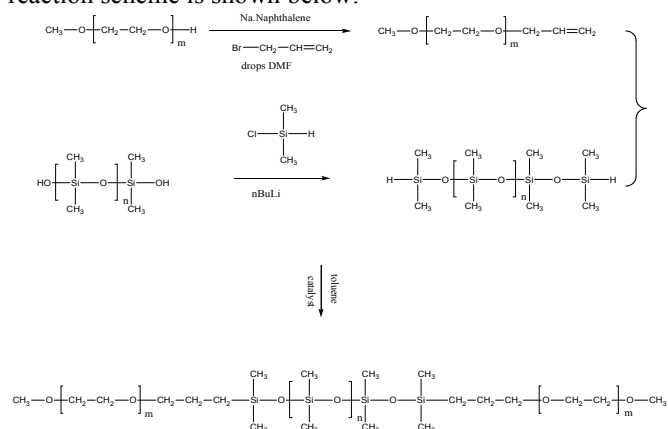


**Characterization:**

The polymer was analyzed by size exclusion chromatography (SEC) and NMR to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from <sup>1</sup>H-NMR spectroscopy by comparing the peak area of the siloxane protons at about 0.08 ppm with the peak area of ethylene oxide protons at about 3.4 ppm. The hydrosilylation reaction is monitored by FTIR, the disappearance of SiH at 2125 cm<sup>-1</sup>.


**Solubility:**

The polymer is soluble in THF, not soluble in MeOH, ether and hexane.

**NMR of PDMS2SiH**

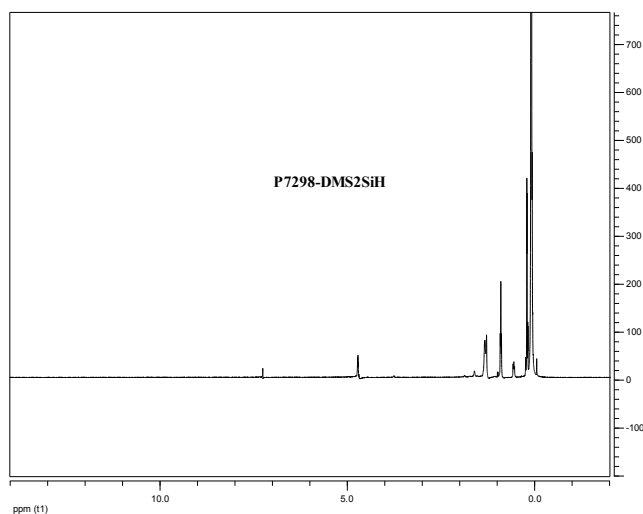


**<sup>1</sup>H-NMR Spectrum of the final block copolymer:**

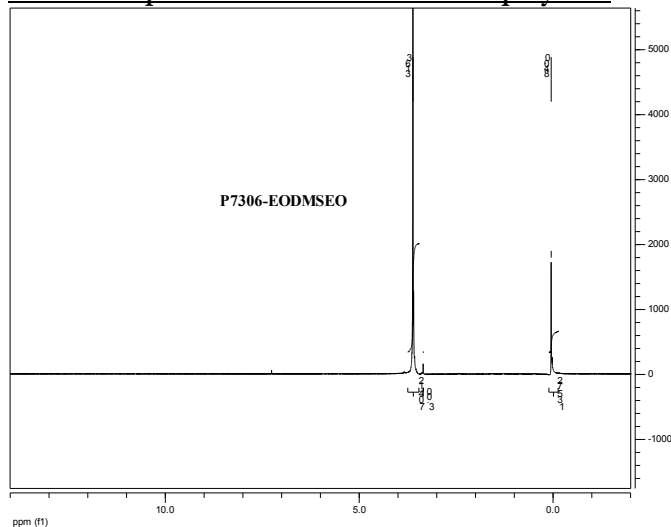

**SEC of the polymer**

**P7306-EODMSEO**

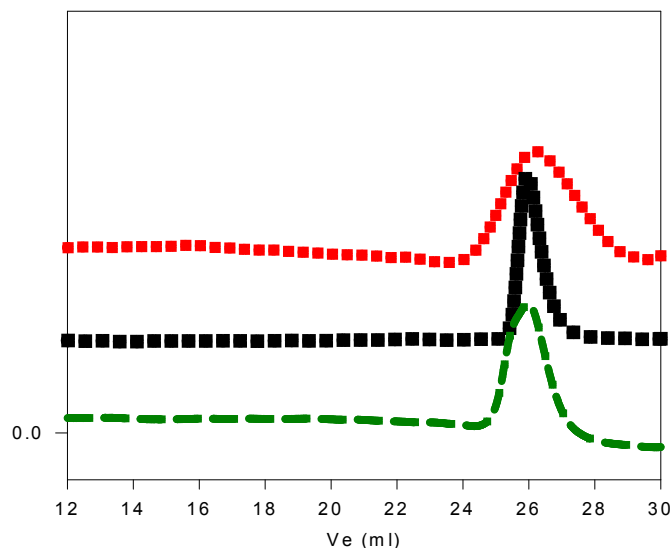

Size exclusion chromatography of the polymer

■■■■ PDMS-2SiH: Mn=2000, Mw=2400, PI=1.2

■■■■ Ally PEO, Mn=5000, Mw=5500, PI=1.1

■■■■ Final block copolymer:  
PEO(5000)-b-PDMS(2000)-b-PEO(5000), PI=1.2  
Composition from <sup>1</sup>HNMR


## Thermal analysis of the sample# P7306-EODMSEO

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature ( $T_g$ ).

### Thermal analysis results at a glance

For PDMS block		
$T_g$ : Not found (-127°C lit. value)	$T_m$ : -	$T_c$ : -
For PEO block		
$T_g$ : -52°C	$T_m$ : 59°C	$T_c$ : 34°C


### Thermogram for PEO block:

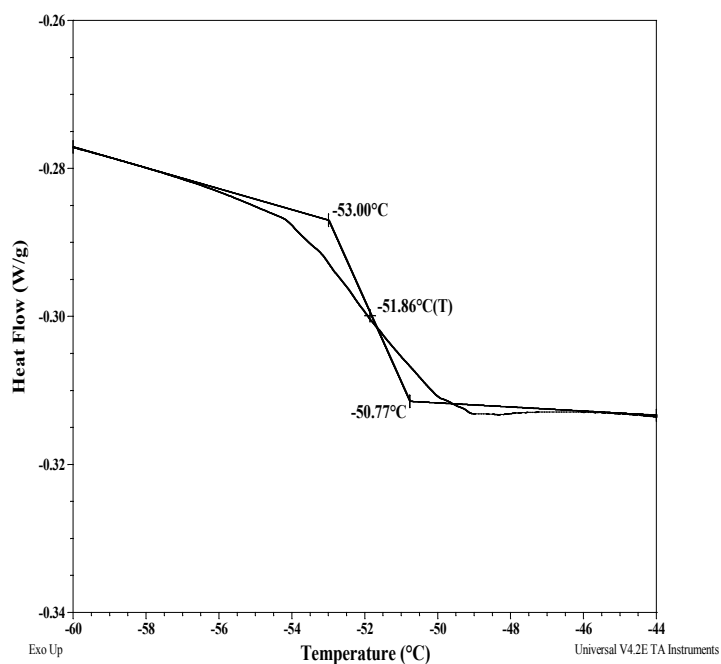

## Melting and crystallization curve for the sample

The melting temperature ( $T_m$ ) was taken as the maximum of the endothermic peak where as the crystallization temperature ( $T_c$ ) was considered as the minimum of the exothermic peak.

### Melting curve for PEO block:

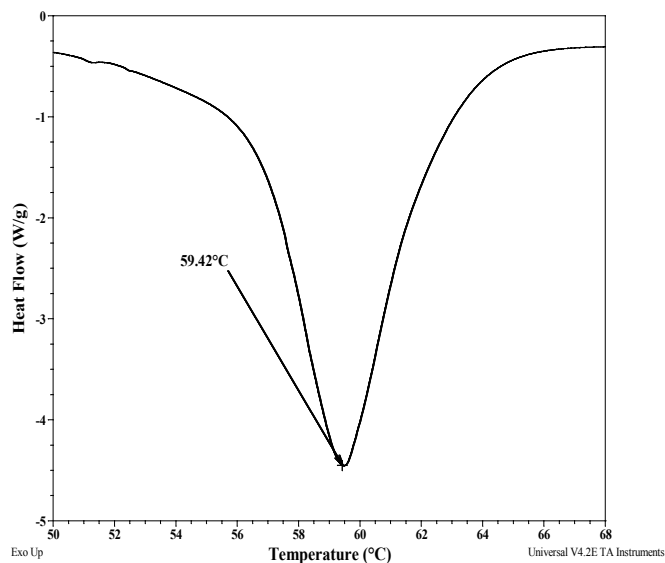

### Crystallization curve For PEO block:

