


Sample Name:

Four arm Poly(ethylene oxide –b-ε-caprolactone)


Sample #: P10704A-4EOCL

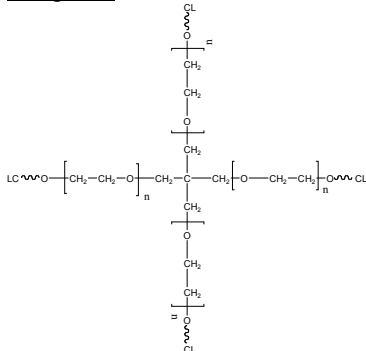


Mn x 10 ³ Total (branch)	PDI
0.72-b-1.95 Mn: (0.19.-b-0.48)	1.15
Dp of each branch: EO-b-CL 4.0-b-4.2(average)	

Synthesis Procedure:


The polymer was prepared by ring opening polymerization of caprolactone using Tin octoate as the catalyst and pentaerythritol ethoxylate that bears Mn of 320. The scheme of the reaction is illustrated below:

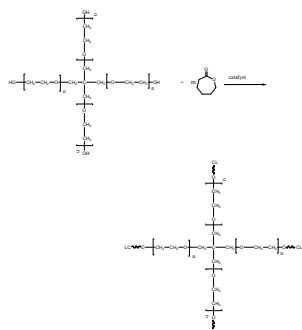


Characterization data for the core bearing Mn : 320

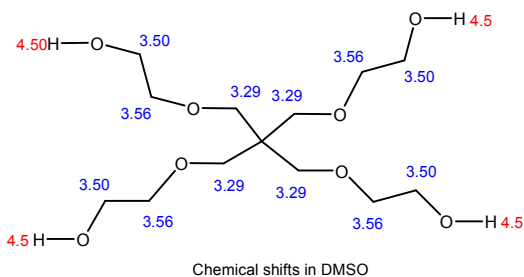


¹H NMR of the core:

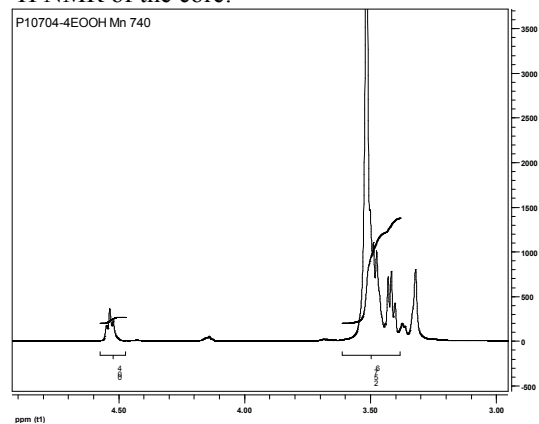

¹H NMR of the Polymer:

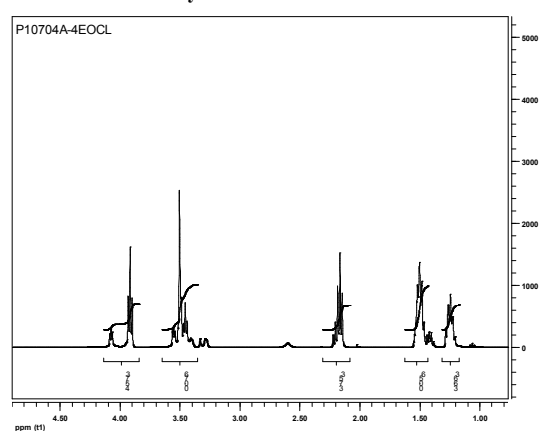

SEC of the polymer:

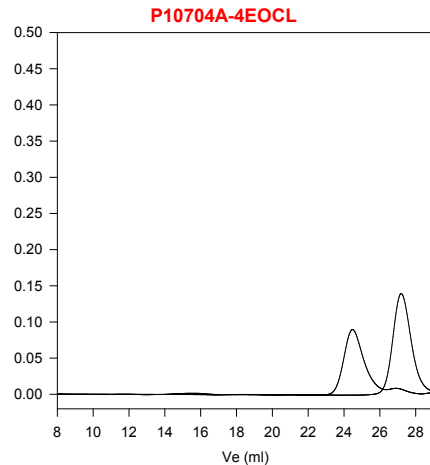

Size Exclusion Chromatogram of
core based on pentaerythritol ethoxylate

— Core : M_n=720 M_w=830, M_w/M_n=1.15
4EOCL
Mn : 720-b-1950 Mw/Mn 1.15
Dp of each branch: EOCL: 4.0-b-4.2

Characterization.

The Mn of the polymer is calculated from ¹H-NMR spectroscopy by comparing the peak area of the core protons at about 4.5 ppm with the ε-caprolactone protons at about 4.1 ppm. Polydispersity is determined by size exclusion chromatography (SEC): Varian liquid chromatograph equipped with UV and refractive detector. SEC columns from Supelco were used with THF containing 2 vol% (Et)₃N as the eluent.